

Synthesis of Mg-Ni-Zn ferrite Nanoparticles by Sol Gel auto combustion route and study of its structural and morphological characteristics

Mane Aparna T^{1,4}, Mane Avinash T¹, Mane TR², Bobade DH³ and Shinde DP⁴

¹Research scholar, J. J. T. University Jhunjhunu; Rajasthan

²Physics Department; Sangola College, Sangola, Solapur (M.S)

³Physics Department, C. T. Bora College, Shirur, Pune (M. S)

⁴Physics Department, K. B. P. College, Pandharpur, Solapur (M.S)

Email: aparnamane10496@gmail.com

Manuscript Details

Available online on <https://www.irjse.in>

ISSN: 2322-0015

Editor: Dr. Arvind Chavhan

Cite this article as:

Mane Aparna T, Mane Avinash T, Mane TR, Bobade DH and Shinde DP. Synthesis of Mg-Ni-Zn ferrite Nanoparticles by Sol Gel auto combustion route and study of its structural and morphological characteristics, *Int. Res. Journal of Science & Engineering*, 2023, Special Issue A12: XX-XX.

Article published in Special issue of International Conference on "Recent Trends in Materials Science, Synthesis, Characterization and Applications (RTMS-2023)" organized by Department of Physics, Anekant Education Society's, Tuljaram Chaturchand College of Arts, Science and Commerce, Baramati, Dist Pune, Maharashtra, India (Autonomous) date, January 3-4, 2023.



Open Access This article is licensed under a Creative Commons Attribution 4.0 International License, which permits use, sharing, adaptation, distribution and reproduction in any medium or format, as long as you give appropriate credit to the original author(s) and the source, provide a link to the Creative Commons license, and indicate if changes were made. The images or other third party material in this article are included in the article's Creative Commons license, unless indicated otherwise in a credit line to the material. If material is not included in the article's Creative Commons license and your intended use is not permitted by statutory regulation or exceeds the permitted use, you will need to obtain permission directly from the copyright holder. To view a copy of this license, visit <http://creativecommons.org/licenses/by/4.0/>

Abstract

Nanoparticles of Magnesium Nickel Zinc ferrite with general formula $Mg_{0.6-x}Ni_xZn_{0.4}Fe_2O_4$ (where $x = 0.3$) have been synthesized by using sol gel auto combustion route. The prepared powder was sintered at 150°C, 300°C and 450°C for 1 hour duration. By using different physical and chemical methods, structural and morphological characteristics of prepared sample were studied. The X-ray diffraction method was used for the confirmation of single-phase cubic spinel structure. Also, this method was used to calculate lattice parameter, x-ray density, bond length (A - O and B - O), ionic radii (R_A and R_B) and particle size. As temperature increases from 150°C to 450°C, the lattice constant (a) increases from 8.3117 to 8.3744 Å and also crystalline size decreases from 38 nm to 34 nm. By using Scanning Electron Microscope (SEM) image, grain size of prepared compound for different sintering temperatures were determined. The average grain size varies from 300nm to 200nm for increasing sintering temperature. Energy Dispersive Analysis of X-ray diffraction reveals the presence of all the metals in the appropriate composition as used in compound preparation.

Keywords: Nanoparticles, x-ray diffraction, SEM, EDAX, crystalline size, lattice constant, bond length, ionic radii, x-ray density.

Introduction


Many researchers have been studied structural, electrical and magnetic behavior of ferrites in the view of their applications within the range of frequency up to few GHz. Ferrites mostly exhibits spinel structure with general formula AB_2O_4 [1] where A cations are present in tetrahedral sites and B cations are present in Octahedral site. Mainly, Ferrites are the mixed metal oxide with iron oxide as main component [2]. Ferrites have wide applications in microwave devices and magnetic recordings. The study of structural and morphological properties of ferrites reveals its physical and chemical behavior. For making high density information storage devices, nanoferrite materials are most useful [3]. At present, nano-ferrites are most useful material for technological applications and drug delivery [4]. Because of their high electric resistivity and low eddy current loss, ferrite nanoparticles are most important. The ferrites are structure sensitive material [5]. The ferrites containing magnesium and zinc have higher resistivity and it is most useful in high frequency devices [6]. At present, there are several methods which are useful for the preparation of ferrite nanoparticles. Because of its various benefits and easiness in preparation, in the present work, sol-gel auto combustion method is used for the preparation.

Methodology

In the present work, the Mg-Ni-Zn ferrite powder was prepared by sol-gel auto combustion method. The general formula used for preparation is $Mg_{0.6-x}Ni_xZn_{0.4}Fe_2O_4$ (where $x = 0.3$). The required metals used for the preparation were analytical reagent (A.R) grade nitrates such as magnesium nitrate, nickel nitrate, zinc nitrate and ferric nitrate. The citric acid $C_6H_8O_7$ plays an important role as a fuel in the formation of homogeneous mixture of metal cations. The metal nitrate and fuel ratio is used in the proportion 1:3. For the formation of sol, all metal nitrates and fuel citric acid were dissolved in distilled water. The pH of the solution was maintained to 7 by slowly adding ammonia

solution. During this process, the solution was kept continuously stirring by using magnetic stirrer. The stirring of solution was continued till the gel is formed at constant temperature $100^\circ C$. The gel gets converted into ash form after heating at about 4 to 4.5 hours. The prepared powder was crushed using agate mortar to obtain nanoferrite. The prepared powder was sintered at temperature $150^\circ C$, $300^\circ C$ and $450^\circ C$ for 1 hour.

The general chemical reaction:



Result and Discussion

The prepared sample was characterized by using XRD, SEM and EDAX. The results obtained are discussed below;

XRD studies

Figure-1 shows the XRD patterns of composition $Mg_{0.6-x}Ni_xZn_{0.4}Fe_2O_4$ (where $x = 0.3$). The study of XRD patterns shows that all the prepared samples are single phase spinel cubic structure [7]. It is found that the Bragg's angles of corresponding peaks in the XRD pattern approximately matches with the characteristics of the reflection peaks of Mg- Ni- Zn ferrites which is reported in JCPDS by Barakat, m et al., J. Therm Anal 37.241 (1991) [8].

Fig. 2 shows variation of lattice constants (a) with temperature. From graph it is seen that lattice constant (a) increases with increases in sintering temperature (T). The metal oxygen bond length (A-O) on tetrahedral site is calculated by using formula

$$A-O = (u - 0.25) \cdot a \cdot \sqrt{3} \text{ ----- (1)}$$

The metal oxygen bond length (B-O) on octahedral site is calculated by using formula

$$B-O = (0.625 - u) \cdot a \text{ ----- (2)}$$

Where, u is known as oxygen ion parameter.

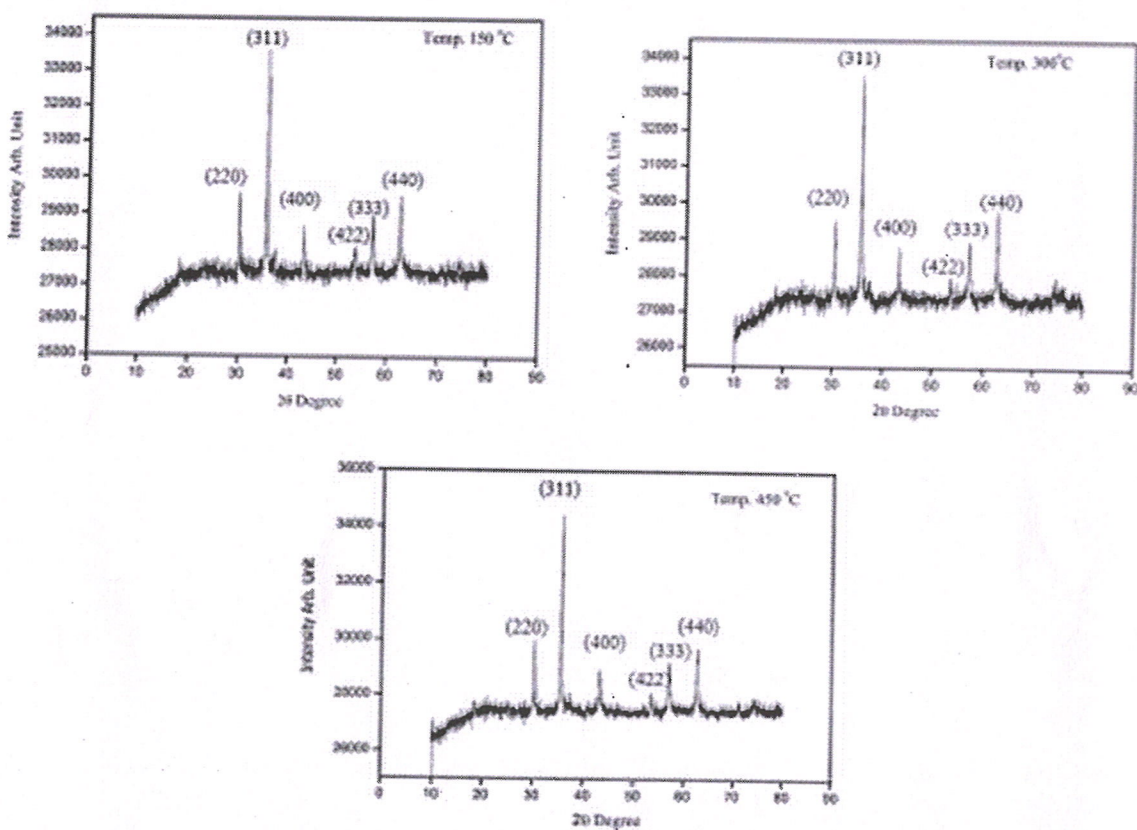


Fig.1: XRD of $Mg_{0.6-x}Ni_xZn_{0.4}Fe_2O_4$ (where $x = 0.3$) for temperatures 150°C, 300°C and 450°C.

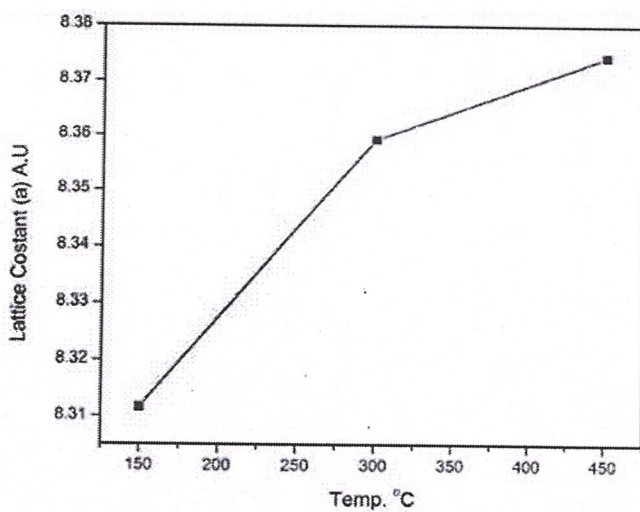


Fig. 2: Lattice Constant (a) Vs Temperature (T)